


# RUST-OLEUM®

INDUSTRIAL

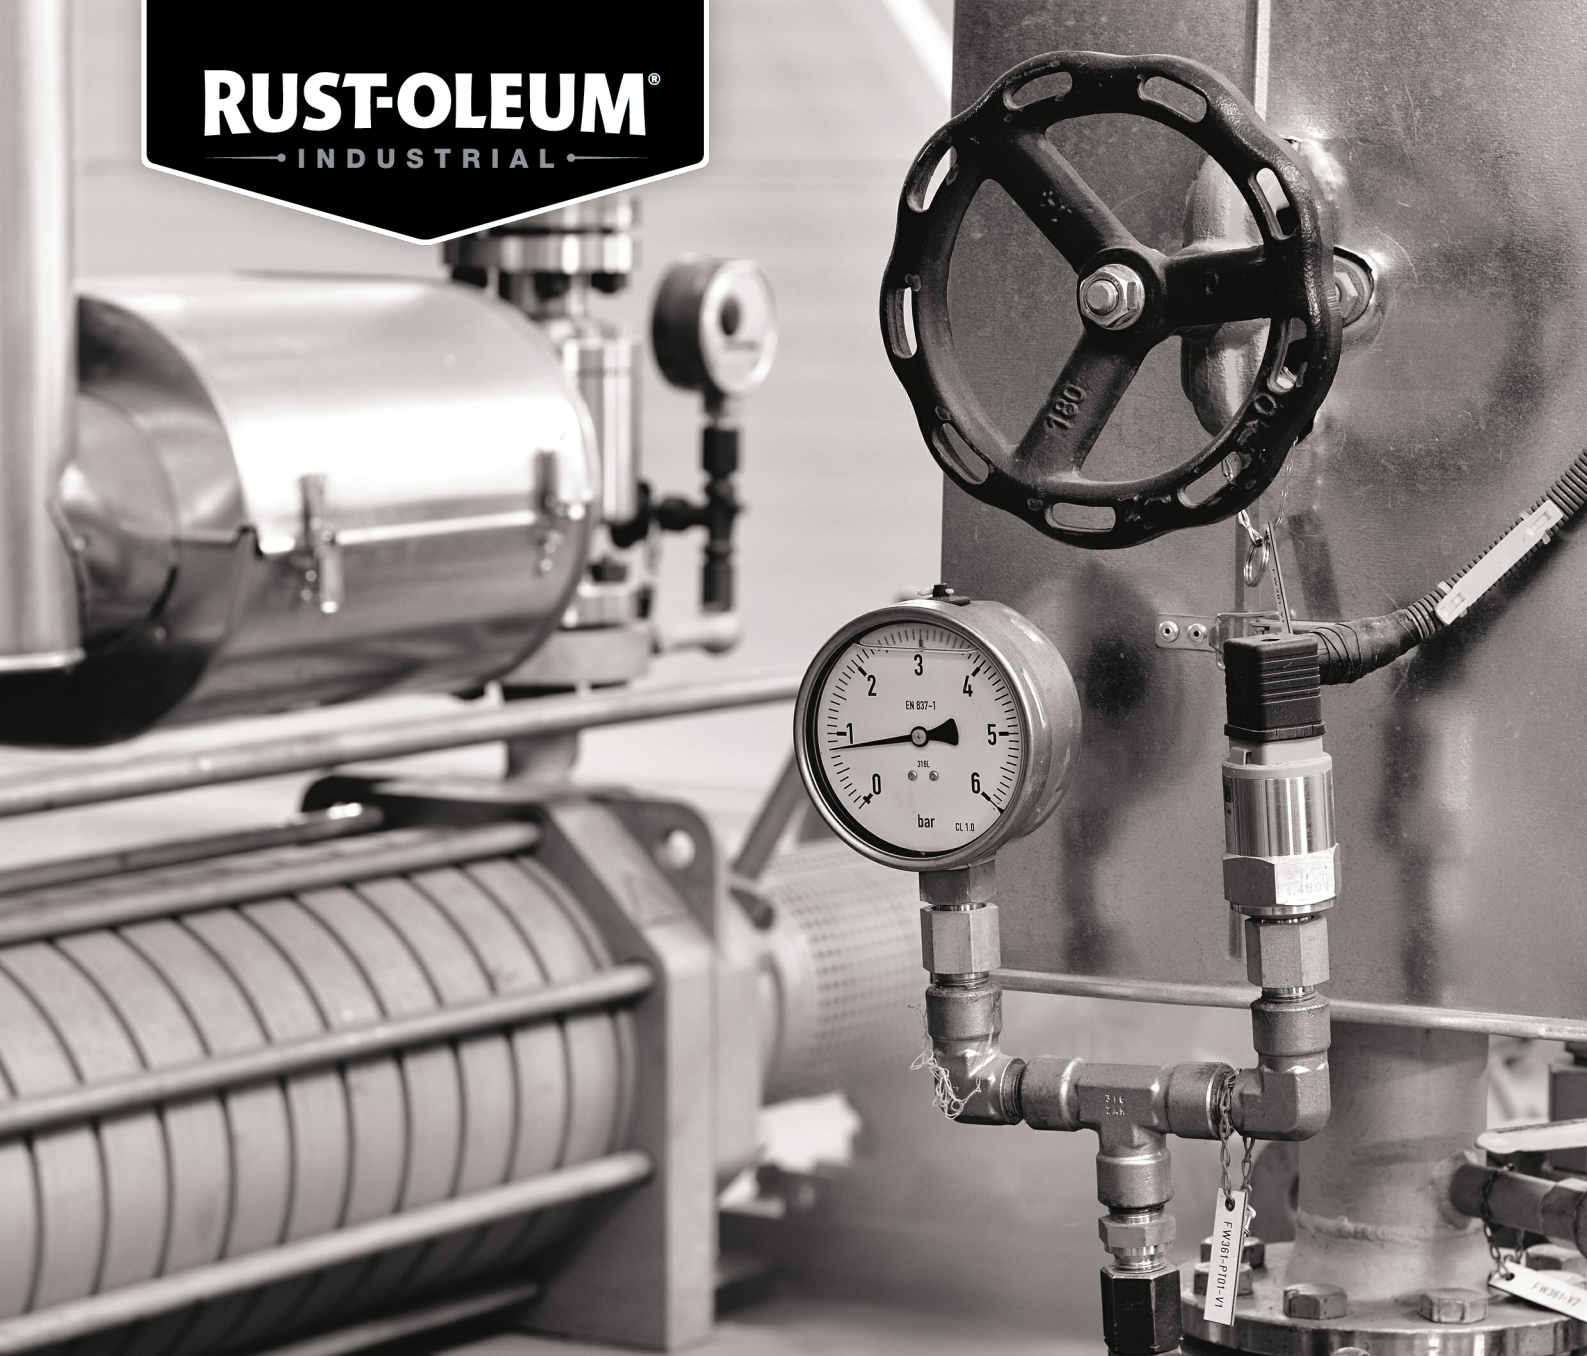

## 4215 HEAT-RESISTANT TOPCOAT

# Heat resistant topcoat

- Long-term continuous heat resistance up to 425°C
- Durable aluminium gloss finish
- One can covers 80m<sup>2</sup>
- Ideal for boiler fronts, incinerators, stacks, kilns and more
- Excellent flow

KNOW-HOW TO PROTECT™

WWW.RUST-OLEUM.EU

# 4215 HEAT-RESISTANT TOPCOAT

## BESKRIVNING

Single pack heat resistant topcoat provides heat resistance up to 425°C dry heat. Nice aluminum finish.

## REKOMMENDERAD ANVÄNDNING

4215 should be used on new, bare steel or blasted steel surfaces primed with 4268 heat resistant primer. Provides heat resistance up to 425°C dry heat in sheltered or interior environments, if applied on Heat-Resistant Primer 4268. On blasted steel two coats of 4268 should be applied prior to the application of 4215.

## TEKNISK DATA

Densitet:	1,14
Glansnivå:	Metallic
Korrosionsklass:	C3 måttlig korrosion
Torrsubstansvolym:	44,6%
Värmebeständighet:	425°C (continuous dry heat)

## TORKTIDER VID 20°C/RELATIV LUFTFUKTIGHET 50%

Beröringstorr:	2 hours
Hanteringstorr:	8 hours
Övermålningsbar:	24 hours
Fullt härdad:	24 hours after minimum service temperature is reached

## REKOMMENDERAD VÅTFILMSTJOCKLEK

34 µm

## REKOMMENDERAD TORRFILMSTJOCKLEK

15 µm

## TEORETISK FÖRBRUKNING

16 m<sup>2</sup>/l

## PRAKTISK FÖRBRUKNING

Practical coverage depends on many factors such as porosity and roughness of the substrate and material losses during application.

## YTFÖRBEREDELSE

Remove grease, oil and all other surface contaminations by alkaline- or high pressure (steam) cleaning in combination with appropriate detergents. Prime with the recommended Primer 4268. Sand previous coatings which are in good condition to roughen the surface slightly. The surface must be clean and dry during application.

## BRUKSANVISNING

To ensure homogeneity, coating materials should be thoroughly stirred prior to use.

## APPLICERINGSFÖRHÅLLANDEN

Temperature of air, substrate and coating material between 5 and 35°C and relative humidity below 85%. The substrate temperature must be at least 3°C above dew point.

## APPLICERING OCH SPÄDNING: PENSEL

Up to 10% volume RUST-OLEUM Thinner 150.

Use natural bristles, long hair brushes.

## APPLICERING OCH SPÄDNING: ROLLER

Up to 10% volume RUST-OLEUM Thinner 150.

Use medium nap, polyamide 8 -12 mm rollers.

## APPLICERING OCH SPÄDNING: AIRLESSPRUTA

If required up to 5% volume RUST-OLEUM Thinner 150.

Pneumatic and electric airless equipment. Tip size: 0.013-0.015 inch (use reverse tips)

Fluid pressure: 110 - 150 bar.

Check wet film thickness, avoid excessive film thickness.

## APPLICERING OCH SPÄDNING: TRYCKLUFTSSPRUTA

10-20% volume RUST-OLEUM Thinner 150.

Gravity cup and pressure cup. Tip size: 1.2 -1.8 mm. Atomizing pressure: 2 - 4 bar.

## RENGÖRING AV UTRUSTNING/SPILLA

Use RUST-OLEUM Thinner 150/160 or aromatic hydrocarbons.

## ANMÄRKNINGAR

Maximum dry film thickness per coat: 30 µm dry, equals 125 µm wet.

Heat up the coating slowly (max. 50°C/hour) until 150 °C.

## SÄKERHETSDATA

VOC-nivå:	499 g/l
VOC färdigmix:	499 g/l
VOC-kategori:	A/i
VOC-gräns:	500 g/l
Anmärkning om säkerhet:	Consult Safety Data Sheet and Safety Information printed on the can. <b>Attention:</b> due to possible gassing first remove carefully the sticker from the lid of the can.

## HÅLLBARHET

Minimum of 5 years from date of production in unopened cans, if stored in dry, well ventilated areas, not in direct sunlight at temperatures between 5° and 35°C.

Utgivet den: 07/02/2025

**Tillgängliga färger och förpackningsstorlekar:** Se respektive produktsida på [www.rust-oleum.eu](http://www.rust-oleum.eu) för en översikt över tillgängliga färger och förpackningsstorlekar.

**Förbehåll:** Informationen i detta produktdatablad är korrekt så långt vi känner till och ges i god tro men utan garanti. Vi förutsätter att användaren självständigt har tagit ställning till lämpligheten av våra produkter för hans eller hennes egna syften. Under inga omständigheter är Rust-Oleum Europe ansvarigt för indirekta skador eller följdsador. Produkterna ska förvaras, hanteras och användas under förhållanden som överensstämmer med Rust-Oleum Europes rekommendationer i den senaste utgåvan av produktdatabladet. Det är användarens ansvar att säkerställa att han/hon har den aktuella utgåvan. Senaste utgåvan av produktdatabladet kan erhållas kostnadsfritt från [www.rust-oleum.eu](http://www.rust-oleum.eu) eller vår Kundtjänst. Rust-Oleum Europe förbehåller sig rätten att ändra egenskaperna i sina produkter utan föregående avisering.

**Rust-Oleum Netherlands B.V.**  
Zilverenberg 16  
5234 GM 's-Hertogenbosch  
The Netherlands  
T : +31 (0) 165 593 636  
F : +31 (0) 165 593 600  
[info@rust-oleum.eu](mailto:info@rust-oleum.eu)

**Tor Coatings Ltd (Rust-Oleum Industrial)**  
Shadon Way, Portobello Ind. Estate  
Birtley, Chester-le-Street  
DH3 2RE United Kingdom  
T : +44 (0)1914 113 146  
F : +44 (0)1914 113 147  
[info@rust-oleum.eu](mailto:info@rust-oleum.eu)

**Rust-Oleum France S.A.S.**  
38, av. du Gros Chêne  
95322 Herblay  
France  
T : +33(0) 130 40 00 44  
F : +33(0) 130 40 99 80  
[info@rust-oleum.eu](mailto:info@rust-oleum.eu)

**N.V. Martin Mathys S.A.**  
Kolenbergstraat 23  
3545 Zelem  
Belgium  
T : +32 (0) 13 460 200  
F : +32 (0) 13 460 201  
[info@rust-oleum.eu](mailto:info@rust-oleum.eu)